

ASTM D5024 Dynamic Mechanical Properties (DMA) of Plastics in Compression

TEST METHOD SUMMARY

ASTM D5024 is one of the most commonly used test standards for conducting DMA of Plastics in Compression. The test procedure characterizes the viscoelastic properties of thermoplastic resins, thermosetting resins and composite systems. Using cylindrical specimens, ASTM D5024 determines the storage (elastic or E'), loss (viscous or E'') and complex (E^*) moduli, as well as $\tan \delta$, as a function of frequency, temperature, or time. These properties provide insights into the thermomechanical performance, including glass transition temperature (T_g), damping behavior, and effectiveness of cure.

NOTE: Data accuracy and analysis is particularly critical with polymers, as failures can occur even when loads and stresses are constant over time. This is known as creep failure. Another common failure occurs when polymer life is shortened due to operation in higher temperatures than originally designed for. In accordance with the Williams-Landau-Ferry (WLF) model, the MTS DMA software can perform time-temperature superposition (TTS) algorithms, allowing materials researchers to generate master curves that are critical in predicting long-term life based on short-term test data. Three decades of reliable data is especially important here since data errors lead to large amounts of error in life estimation.

Solutions for ASTM D5024 typically include these types of components;

LOAD FRAME OPTIONS*

Both the MTS Acumen® and the MTS Landmark® test systems are ideal for conducting dynamic mechanical analysis (DMA) of polymers per ASTM D5024. They offer a variety of force capacities and deliver up to 100 Hz (covering three decades) of precise, frequency controlled test protocols to accommodate a wide variety of DMA and other fatigue testing needs. The compact MTS Acumen systems' electrodynamic actuation consumes less energy than other technologies, and provides a clean, quiet, and cost-effective system operation. The MTS Landmark 100 Hz Elastomer Test System is a tabletop system that features MTS servohydraulic actuation technology, and is the preferred test system when other testing requirements demand higher force capacities.



MTS Acumen®
Electrodynamic Test Systems



MTS Landmark®
100 Hz Elastomer Test System

COMPRESSION PLATEN OPTIONS*

	
<p>50mm Diameter Platen</p>	<p>70mm Diameter Platen</p>
<p>There are two different compression platens that can be used for ASTM D5024. The MTS 50mm Diameter Platen has a temperature range of -150°C to 350°C (-238°F to 662°F). The 70mm Diameter Platen (MTS Model 643.07C) has a temperature range of -40°C to 149°C (-40°F to 300°F) and can accommodate a specimen diameter range of 7.6mm to 76.2mm (0.3" to 3").</p>	



CHAMBER OPTIONS*

651.05F-01 Chamber



To ensure accurate and consistent results, this MTS 651.05 Environmental Chamber has been tested in DMA applications. It is designed to maintain a constant temperature with very little temperature gradient across the specimen. Heating is achieved with electrical heating elements and a motor-driven fan for diffused convection heat. Cooling is accomplished with liquid nitrogen. It also has a built-in temperature controller, all-welded construction, and Fiberglas™ insulation.

SOFTWARE OPTIONS*

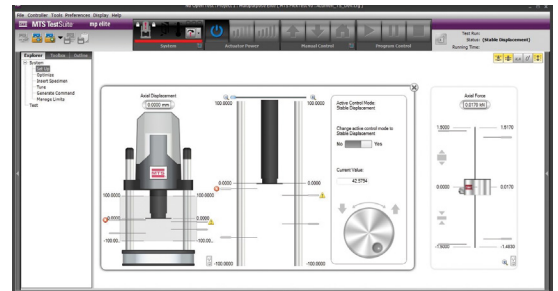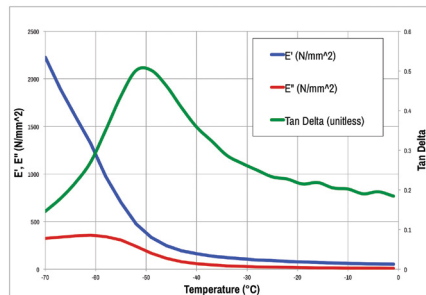

DMA / Dynamic Characterization Application Software

To test per ASTM D5024, application software MTS Model 793.31 DMA/Dynamic Characterization allows the user to conduct dynamic characterization (leveraging the Kelvin-Voigt model) with up to four channels of control. The DMA application software measures Stiffness (K), Phase Angle, Damping (C), Modulus (E or G), Tan Delta, Glass Transition (T_g), and more.

Additional software options include the TTS (time-temperature superposition) Master Curves module, which is commonly used to predict viscoelastic behavior at frequencies outside the range of what is typically achievable with physical testing. And the MTS Model 793.33 for static deflection testing and MTS Elastomer Express (for QA/QC testing).

TestSuite™ Software for MTS Acumen® Systems

MTS TestSuite Multipurpose Software delivers the test definition, execution, analysis and reporting capabilities required for dynamic testing. The intuitive user interface is optimized for MTS Acumen systems. The software lets you graphically build and run tensile, compression, bend, fatigue and fracture, multiaxial, block loading and custom profile tests with efficiency. With its easy-to-use interface, you can easily test to specific industry standards or pursue your own interpretation of a standard with customizable "plug-and-play" test methods. The software also captures all setup data and test results, allowing you to quickly repeat tests, analyze data with the stand-alone Analysis Software, and design and create reports with the convenient Excel Add-In.

*NOTE: This technical note is intended to show some of the popular and more common solutions used for this particular application. Most often, additional options are available and necessary to accomplish your more comprehensive test objectives.

APPENDIX - TEST SPECIMEN DETAIL

The guidance provided in ASTM D5024 allows for test specimens to be cut from molded shapes, or they may be molded to other desired finished dimensions. Most common are cylindrical test specimen is up to 25mm (1.0") in diameter by 5mm (0.2") in height (thickness). Cylindrical specimens of other dimensions can be used but should be clearly identified in the report.



MTS Systems Corporation
14000 Technology Drive
Eden Prairie, MN 55344-2290 USA
Telephone: 1-952-937-4000
Toll Free: 1-800-328-2255
Fax: 1-952-937-4515
E-mail: info@mts.com
www.mts.com

ISO 9001 Certified QMS

MTS, MTS Acumen, and MTS Landmark are registered trademarks, and TestSuite is a trademark of MTS Systems Corporation within the United States. These trademarks may be protected in other countries. RTM No. 211177.

©2017 MTS Systems Corporation
100-336-902a TMTND5024 Printed in U.S.A. 5/17